

HIGHLY HOMOGENEOUS NITROGEN DOPED TITANIA NANOMATERIALS: SYNTHESIS AND CHARACTERIZATION

Nurul Diyana Zainal^a, Hadi Nur^b, Siew Ling Lee^{a,b*}

^aDepartment of Chemistry, Faculty of Science, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia

^bCenter for Sustainable Nanomaterials, Ibnu Sina Institute for Scientific and Industrial Research, Universiti Teknologi Malaysia, 81310 UTM Johor Bahru, Johor, Malaysia

Article history

Received

1 February 2015

Received in revised form


24 March 2015

Accepted

1 August 2015

*Corresponding author
sllee@ibnusina.utm.my

Graphical abstract

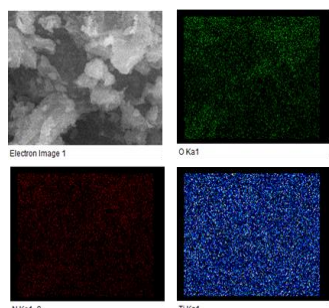

EDX mapping of 5N-TiO₂

Abstract

A series of nitrogen doped titania nanomaterials were synthesized via sol-gel method by using tetraethyl ammonium hydroxide as N source. Doping of N into TiO₂ was confirmed via X-ray diffraction (XRD) and fourier transform infrared spectroscopy (FTIR) analyses. Mixture of anatase and rutile phases appeared in the unmodified TiO₂ which was calcined at 773 K. The addition of N to TiO₂ matrix led to formation of single phase of anatase. It has been demonstrated that TiO₂ and all the N-doped TiO₂ materials were in nanoscale ranging 15.91 – 20.82 nm. Change in surface morphology after N doping was detected by field emission scanning electron microscope (FESEM). Results of EDX mapping analysis indicated homogeneous distribution of N dopants.

Keywords: Titania, nitrogen, nanomaterial, homogeneous

© 2016 Penerbit UTM Press. All rights reserved

1.0 INTRODUCTION

Since its profitable production in the early twentieth century, titanium dioxide (TiO₂) has been extensively used as a pigment in sunscreen, paints, toothpaste [1-3]. Nanomaterials of titanium dioxide have been receiving much attention for their good photocatalytic and hydrophilic properties [4-5]. These works on application and fundamental aspects of TiO₂ are mainly related to the self-cleaning, chemical energy generation, and photovoltaic devices. Titania has advantages including being non-poisonous, easy to prepare, inexpensive and strong oxidation-reduction reactions [6]. It could restrain virus activity and eliminates the planktons in the air [7]. Titania has also the features of anti-pollution, deodorisation, dust-proof, and self-clean and currently great interest has

been dedicated to the use of TiO₂ based photocatalyst for the degradation of dyes in aqueous solutions[8]. The benefit derived from TiO₂ and doped TiO₂ have drawn much research in the field.

Different methods are available for the preparation of TiO₂ photocatalysts, such as hydrothermal [9], solvothermal [10], direct oxidation [11], chemical vapor deposition [12], physical vapor deposition [13], electrodeposition[14], sol [15] and sol-gel [16-17]. Nonetheless, the advantages derived from preparation of TiO₂ using sol-gel method, which include effective control of particle size, shape and properties, synthesis of nanocrystalline powder with high purity at low temperature, better homogeneity of raw materials, preparation of composite materials, and production of homogeneous materials have motivated many researchers to the use of the method in preparing TiO₂ [18-19].

The sol-gel method is a wet-chemical technique widely employed in making various ceramic materials [18]. In a typical sol-gel process, hydrolysis and polymerization of precursors will form a colloidal suspension or sol. The liquid phase to solid gel phase transition occurs after complete polymerization [19]. Many studies reported that different modifications of sol-gel method have been used to produce pure thin films or powders in large homogeneous concentration [17].


Doping with non-metal such as nitrogen seems to be more successful [20]. The introduction of substitutional N atoms into the TiO₂ matrix improves optical absorption in the visible region, leading to corresponding photochemical activity. The solar energy contains only 3-4% of UV light ($\lambda < 380\text{nm}$), while the visible light made up of 47% [21]. Thus, many new approaches have been carried out by researchers to enhance the nanomaterials efficiency in visible light region. Successful evidence in various researches shows that modification of titania nanomaterials by doping could enhance the absorptivity of intensity in visible region. Development of TiO₂ responsive to visible light by doping it with various anions as a substitute for oxygen in the TiO₂ lattice has been ongoing studied. The mixing of the p states of the doped non-metal (anions) with O 2p states shifts the valence band edge upwards which narrowed the band gap of TiO₂ with conduction band [22]. Unlike metal ions, non-metal are less likely to recombine, thus non-metal ions contributes to better enhancing ability of the photocatalytic activity of titania. In this work, an attempt was carried out to synthesize homogeneous N-doped titania nanomaterials via sol-gel method. The properties of these materials were presented in this paper.

2.0 METHODOLOGY

N-doped TiO₂ Preparation. A series of N-doped TiO₂ materials were synthesized via sol gel method as shown in Scheme 1. Firstly, tetraethyl ammonium hydroxide (TEAOH, 40% w/w) as N source was mixed with ethanol with mol ratio 1:20. After 5 minutes stirring, the solution was added with titanium tetrakisopropoxide (TTIP, >97%) at N mol% of 1 - 5. The mixture underwent constant stirring at room temperature until the hydrolysis was fully completed after one hour. The gel then was left ageing for 15 hours or up to several days at room temperature until the gel was completely dry. The dried material underwent calcination in air at 773 for 5 hours. The samples were notated as xN-TiO₂, x refers to mol% of N in the sample.

For comparison purpose, pure TiO₂ was also prepared via sol gel method. Typically, TTIP was mixed with acetylacetone and ethanol. The mixture underwent constant stirring until gel was formed. After drying process, the gel was calcined at 773 K for 5 hours.

Characterizations. The prepared N-doped TiO₂ were characterized using X-ray diffraction (XRD), fourier transform infrared (FTIR) spectroscopy, nitrogen adsorption-desorption analysis, field emission scanning electron microscopy (FESEM) and energy dispersive x-ray spectroscopy (EDX). The properties of the materials including crystal structure, crystallinity, crystallite size, surface morphology and sample's homogeneity were examined.

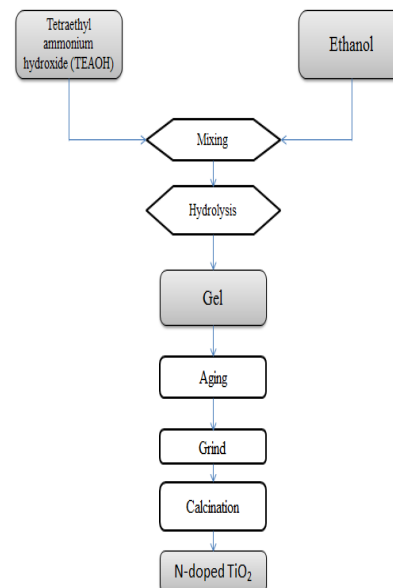

Scheme 1 Preparation of N-TiO₂

3.0 RESULTS AND DISCUSSION

Synthesis of TiO₂ and N-TiO₂ nanomaterials. All synthesized samples were white and fine powder. Figure 1 shows the XRD patterns of TiO₂ and N-doped TiO₂ which were calcined at 773 K. Mixture of anatase and rutile phases appeared in the unmodified TiO₂ which was calcined at 773 K. The diffraction peaks at $2\theta = 25.3^\circ, 37.7^\circ, 48.0^\circ, 53.8^\circ$ and 54.9° were corresponded with typical pattern of anatase-type TiO₂. Meanwhile, the peak at $2\theta = 27.4^\circ$ was associated to rutile phase. Apparently, introduction of N to TiO₂ has retarded the formation of rutile phase. Rao *et al.* [20] reported that the presence of dopants inhibited the anatase-rutile transformation by stabilizing the anatase phase. As evidenced, only pure anatase phase was obtained in the N doped TiO₂ samples. It has been previously reported that N doping hindered anatase-rutile transformation by O vacancies formation [21]. The N dopant ions could enter the anatase lattice and influenced the level of oxygen vacancies, thereby inhibiting the transformation anatase to rutile. Crystallite size of the materials was calculated using Scherrer equation (Table 1). The results showed that TiO₂ and all the N-doped TiO₂ materials were in nanoscale ranging 15.91 – 26.82 nm.

The crystallite size of the N-doped materials decreased with increasing of N dopant amount in the samples, implying that the incorporation of N ions suppressed the growth of TiO₂ nanomaterials. This phenomenon could be explained by smaller ionic radii of N as compare to that of Ti. N atoms substitute for the O atoms in TiO₂ lattice to form O-Ti-N because N is only ~6% larger than O [21].

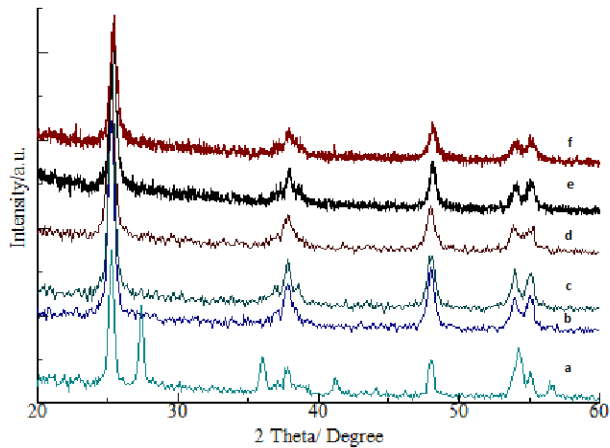


Figure 1 XRD patterns of (a) TiO₂, (b) 1N-TiO₂, (c) 2N-TiO₂, (d) 3N-TiO₂, (e) 4N-TiO₂ and (f) 5N-TiO₂

Table 1 Crystalline size of TiO₂ and nitrogen doped TiO₂ calculated using Scherrer equation

Sample	Crystalline size (nm)
TiO ₂	20.13
1N-TiO ₂	20.82
2N-TiO ₂	20.41
3N-TiO ₂	16.10
4N-TiO ₂	15.93
5N-TiO ₂	15.91

Figure 2 shows FTIR spectra of all the samples. Several broad bands centered at 500-700 cm⁻¹ were due to vibration of Ti-O bonds in TiO₂ lattice. Peaks at ~1633 cm⁻¹ and ~3446 cm⁻¹ were assigned to the residual of adsorbed water. The weak band at around 1360 cm⁻¹ could be attributed to nitrogen oxide species, thus confirming the successful loading of N into TiO₂.

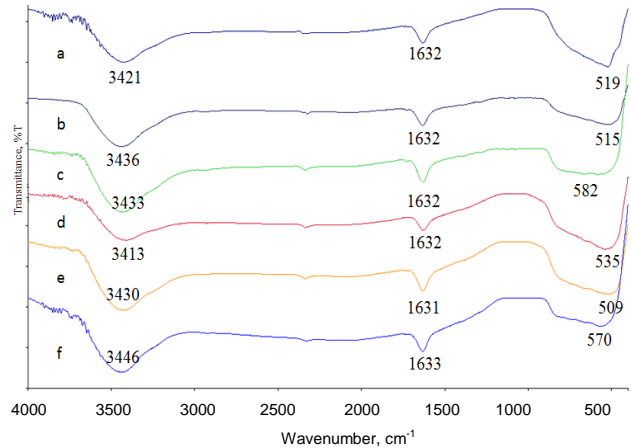


Figure 2 FTIR spectra of (a) TiO₂, (b) 1N-TiO₂, (c) 2N-TiO₂, (d) 3N-TiO₂, (e) 4N-TiO₂ and (f) 5N-TiO₂

Homogeneity of N-doped TiO₂. Morphology and the dispersion of particles were determined by using FESEM and energy dispersive X-ray analysis (EDX), respectively. Figure 3 depicts the FESEM images of TiO₂ and 5N-TiO₂. Figure 3 shows that TiO₂ has smooth surface, which most probably indicated aggregation of TiO₂. Meanwhile, 5N-TiO₂ has rough surface, implying dispersion of nitrogen onto the surface of titania. The EDX mapping image verified successful doping of nitrogen into TiO₂ (Figure 4). The nitrogen was homogeneously dispersed at TiO₂ surface.

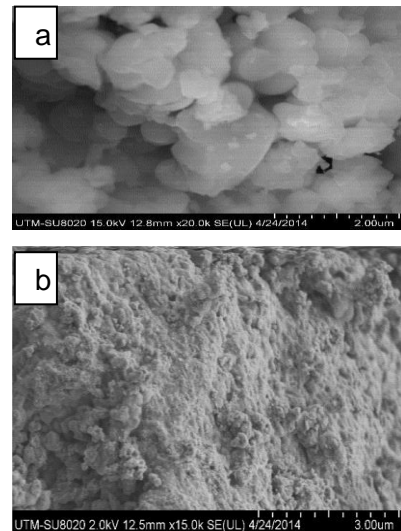


Figure 3 FESEM images of (a) TiO₂ and (b) 5N-TiO₂

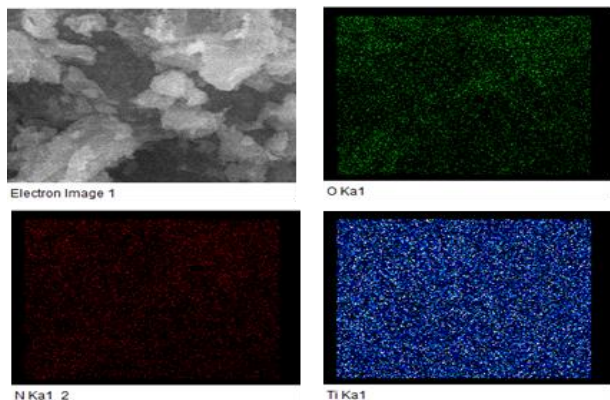


Figure 4 EDX mapping of 5N-TiO₂

4.0 CONCLUSION

The synthesis of homogeneous nitrogen doped titania nanomaterials were successfully synthesized via sol gel method. These N-doped TiO₂ crystallized in pure anatase phase with crystallite size ranged 15.91 – 20.82 nm. TiO₂ has smooth surface while N-doped titania has rough surface, indicating dispersion of nitrogen on the surface of titania. Homogenous dispersion of N was confirmed through the EDX analysis.

Acknowledgement

This work was supported by the Ministry of Higher education, Malaysia and Universiti Teknologi Malaysia (UTM) through Research University Grant (vote number: Q.J130000.2526.10H54) and Fundamental Research Grant Scheme (vote number: R.J130000.7809.4F527). The authors also thank the Center for Sustainable Nanomaterials, Ibnu Sina Institute for Scientific and Industrial Research, UTM for the research facilities.

References

- [1] S. M. Gupta, M. Tripathi. 2011. A Review Of TiO₂ Nanoparticles. *Chinese Science Bulletin.*, 56(16): 1645-1651.
- [2] P. Pichat. 2013. *Photocatalysis And Water Purification: From Fundamentals To Recent Applications.* 2nd Edition. New York: Wiley-VCH.
- [3] J. M. Ekhsan, S. L. Lee, H. Nur. 2014. Niobium Oxide And Phosphoric Acid Impregnated Silica-Titania As Oxidative-Acidic Bifunctional Catalyst. *Applied Catalysis A: General.* 471: 142-148.
- [4] S. L. Lee, H. Nur, S. C. Wei. 2012. Effect Of Acid Treatment On Silica-Titania Aerogel As Oxidative-Acidic Bifunctional Catalyst. *Applied Mechanics and Materials.* 110-116: 457-464.
- [5] N. Attan, H. Nur, J. Efendi, H. O. Lintang, S. L. Lee, I. Sumpono. 2012. Well-Aligned Titanium Dioxide With Very

- High Length To Diameter Ratio Synthesized Under Magnetic Field. *Chemistry Letter.* 41: 1468-1471.
- [6] S. L. Lee, H. Nur, P. W. Koh, J. M. Ekhsan, S. C. Wei. 2011. Synthesis And Characterization Of Acid Modified Silica-Titania Aerogel As Oxidative-Acidic Bifunctional Catalyst. *International Journal of Applied Physics and Mathematics.* 1: 43-47.
- [7] N. H. M. Ran, L. Yuliaty, S. L. Lee, T. M. I. Mahlia, H. Nur. 2013. Liquid-gas Boundary Catalysis By Using Gold/Polystyrene-Coated Hollow Titania. *Journal of Colloid and Interface Science.* 394: 490-497.
- [8] P. W. Lee, S. T. Ong, Y. T. Hung, S. L. Lee. 2013. Photodegradation Of Malachite Green By Immobilization Of Titanium Dioxide, TiO₂ On Glass Plates. *Asian Journal of Chemistry.* 25(2): 755-758.
- [9] J. G. Yu, W. G. Wang, B. Cheng, and B. L. Su. 2009. Enhancement Of Photocatalytic Activity Of Mesoporous TiO₂ Powders By Hydrothermal Surface Fluorination Treatment. *Journal of Physical Chemistry C.* 113(16): 6743-6750.
- [10] W. A. Wang, Q. Shi, Y. P. Wang, J. L. Cao, G. Q. Liu, P. Y. Peng. 2011. Preparation And Characterization Of Iodine-Doped Mesoporous TiO₂ By Hydrothermal Method. *Applied Surface Science.* 257(8): 3688-3696.
- [11] C. He, B. Tian, J. Zhang. 2010. Thermally Stable SiO₂-Doped Mesoporous Anatase TiO₂ With Large Surface Area And Excellent Photocatalytic Activity. *Journal of Colloid and Interface Science.* 344(2): 382-389.
- [12] R. Long, Y. Dai, B. Huang. 2009. Structural And Electronic Properties Of Iodine-Doped Anatase And Rutile TiO₂. *Computational Materials Science.* 45(2): 223-228.
- [13] J. Nowotny, T. Bak, M. K. Nowotny, L. R. Sheppard. 2007. Titanium Dioxide For Solar-Hydrogen IV. Collective And Local Factors In Photoreactivity. *International Journal of Hydrogen Energy.* 32(14): 2609-2629.
- [14] H. Yu, J. Yu, B. Cheng, J. Lin. 2007. Synthesis, Characterization And Photocatalytic Activity Of Mesoporous Titania Nanorod/Titanate Nanotube Composites. *Journal of Hazardous Materials.* 147: 1-2: 581-587
- [15] D. F. Ollis. 2000. Photocatalytic Purification And Remediation Of Contaminated Air And Water. *Chemistry.* 3: 405-411.
- [16] G. Xomeritakis, C. Y. Tsai, Y. B. Jiang, C. J. Brinker. 2009. Tubular Ceramic-Supported Sol-Gel Silica-Based Membranes For Flue Gas Carbon Dioxide Capture And Sequestration. *Journal of Membrane Science.* 341: 30-36.
- [17] M. T. Dulay, J. P. Quirino, B. D. Bennett, R. N. Zare. 2002. Bonded-phase Photopolymerized Sol-Gel Monoliths For Reversed Phase Capillary Electrochromatography. *Journal of Separation Science.* 25: 3-9.
- [18] J. D. MacKenzie. 2003. Sol-gel Research—Achievements Since 1981 And Prospects For The Future. *Journal of Sol-Gel Science and Technology.* 26: 23-27.
- [19] D. Levy. 1997. Synthesis Of Photochromic Chelating Spiroanthoxazines. *Molecular Crystal and Liquid Crystal.* 297: 31-39.
- [20] C. H. R. Rao, A. Turner, J. M. Honig. 1959. The Effect Of Impurities On The Anatase-Rutile Transformation. *Journal of Physical Chemistry. Solids.* 11: 173.
- [21] F. Peng, L. F. Cai, L. Huang, H. Yu, H. J. Wang. 2008. Preparation Of Nitrogen-Doped Titanium Dioxide With Visible-Light Photocatalytic Activity Using A Facile Hydrothermal Method. *Journal of Physics and Chemistry of Solids.* 69(7): 1657-1664.
- [22] J. X. Li, J. H. Xu, W.-L. Dai, H. Li, K. Fan. 2008. One-Pot Synthesis Of Twist-Like Helix Tungsten-Nitrogen-Codoped Titania Photocatalysts With Highly Improved Visible Light Activity In The Abatement Of Phenol. *Applied Catalysis B.* 82(3-4): 233-243.